

# An analysis of the properties of recycled PET fiber-gypsum composites

Seda ERDEM<sup>1</sup>, Nihal ARIOĞLU<sup>2</sup>

<sup>1</sup> erdemsed@itu.edu.tr • Department of Architecture, Faculty of Architecture, Istanbul Technical University, Istanbul, Turkey

<sup>2</sup> nihalarioglu@beykent.edu.tr • Department of Architecture and Engineering, Faculty of Architecture and Engineering, Beykent University, Istanbul, Turkey

*Received: April 2016 • Final Acceptance: February 2017*

## Abstract

The production of composites materials has gained importance due to the increasing and more complex needs of today. Materials used for composites, where the aim is to produce products that have better properties compared to the components forming the main body, can be composed of products obtained from raw materials or recycled products. By adding PET fibers, which are among recycled products, into the composites, the use of limited raw material resources and the harm to the environment during the processes during the lifecycle of the product is minimized. Additionally, gypsum, which is used as matrix in the composite, is easily obtainable, has adequate raw material resources, is easily given form, produces a clean-flat surface, has sufficient tensile and compressive strength and is a good humidity equalizer and sound regulator. However, gypsum has a low impact strength and toughness value. As it is necessary to increase its impact resistance, some research is carried out to this end. In this study, composite material is produced by adding polyethylene terephthalate fibers that are recycled products manufactured from recycled PET bottles and which have not been tried before and PVA based adherence-enhancing additive into the gypsum matrix to improve the properties of gypsum. Test results show that with the addition of fiber the flexural strength of gypsum has somewhat decreased but the addition of the adherence-enhancing additive has considerably increased the compressive and flexural strength. As expected from fiber reinforced composites, the impact and toughness values of the material has considerably increased. The positive effect of the adherence additive between the gypsum matrix and the fiber is clearly visible in the micro analysis carried out.



doi: 10.5505/ituajfa.2017.70288

## Keywords

Composites, Gypsum, Recycled PET fibers.

## 1. Introduction

The energy used in the production, usage and elimination phases of new materials is quite high. Besides, raw material resources found in nature is quite limited. Additionally, the processes present in the lifecycle of the material create soil, water and air pollution and the environment is damaged. The efforts to avoid these damages, eliminate them and minimize the usage of resources increase the importance of recycling.

Recycling lowers the resources required during the production process, preserves the energy required during production and transportation and reduces the damage to the environment caused by the lifecycle of the products (Lei et al., 2009). Recycling is important because of both ecological and economic reasons.

The price of materials obtained through recycling methods are relatively cheaper than materials produced out of raw materials (Parres et al., 2009).

Today, polymers, which are one of the most widely used materials, remain in nature without decaying for many years. As their waste causes pollution, it is necessary to recycle them. The production of PET bottles made of polyethylene terephthalate is increasing every year in relation to the welfare level and consumption. While in 2012 the manufacture of PET bottles in Turkey was 3,8 billion liters, it is believed to be approximately 4.1 billion liters in 2013 (<http://www.suder.org.tr>). The yearly consumption of PET in the world is approximately 13 million tons (Ahmad et al., 2008). Although the consumption of the PET bottles is high, waste PET bottles can now be recycled with chemical and mechanical methods and recycled material obtained from waste PET bottles are reused in the textile, information and construction sectors.

On the other hand, gypsum is one of the traditional building materials with a wide range of use; it is used for centuries for functions such as acoustic insulation and separating wall elements. Although gypsum is a material that is easily obtainable, is cheap, has sufficient mechanical resistance strength as well as humidity equalizer and

brittle behavior properties, its impact strength is low.

The main aim of this study is to improve the brittleness and the impact strength of the gypsum composite material that may be used in buildings and to recycle rPET fibers and to research the possibilities of producing new composite materials from these fibers and gypsum. The study is experimental and the mechanical and physical properties of the composites developed are determined by SEM analysis which are advanced technical analysis.

Thus, it is believed that for the gypsum composites, a contribution is made to increasing its performance as a building material and by using rPET fibers a contribution is made to the improvement of economic and ecologic conditions.

## 2. Experimental

### 2.1. Materials and technical testing

Physical and mechanical tests of composites were made at the Materials Laboratory of the Faculty of Architecture, Istanbul Technical University. Molding plaster preferred for building interiors and made of  $\beta$ -calcium sulfate hemihydrate ( $\beta$ -CaSO<sub>4</sub>.1/2 H<sub>2</sub>O) was used in the tests. Recycled polyethylene terephthalate fibers were used as reinforcement phase in the composite. During the production phase of the preparatory work carried out with the staple fibers created as the end-product by the company that procured fiber, it was observed that rPET fibers were not dispersed homogeneously in the gypsum paste. This time, products that did not undergo finishing in the production process, that were moist and uncut with diameters of 3,3 and 6,6 dtex were obtained from the supplier. A homogeneous dispersion was achieved in the studies that were made with this product whose qualifications were defined. In the main experiments, critical fiber length of these fibers in the composite was calculated and the fibers were cut in the laboratory into 10 mm lengths in accordance with this calculation.

During the sample production, it was determined that the setting duration of gypsum was inadequate for the preparation and molding of the samples. Due to this, citric acid (C<sub>6</sub>H<sub>8</sub>O<sub>7</sub>)

was added to the mixture at the ratio of 0,025% of the weight of the gypsum to delay the setting of the gypsum. Additionally, PVA based adherence-enhancing additive was added to the mixture at the ratio of 5% of the weight to increase the adherence between the gypsum matrix and the rPET fibers. During the sample production, when the rPET fibers were first added to gypsum powder and then water was added, the fibers were not dispersed homogeneously. This time gypsum paste and rPET fibers were first mixed with the help of a mixer. However, during the process of mixing, the fibers stuck to the mixer and lumps were formed and it was observed that they, again, were not dispersed homogeneously. As it was emphasized in the literature (Arioğlu et al., 2008) that the fibers had a structure prone to forming lumps in a dry mixture, this time the fibers were left in water before the mixing process and thus it was ensured that they were dispersed homogeneously in water. Rest of the materials (gypsum powder, polymer additive and citric acid as a retarder) were added to the mixture and they were mixed manually and a homogeneous mixture was obtained.

The ratio of the fibers in the mixtures were determined as 0.05%, 0.075%, 0.1%, 0.15%, 0.2%, 0.25%, 0.5% and 1%. Samples with more than 1% fiber volume (2% and 5%) were also prepared but production was stopped as the dispersions were not homogeneous in these samples.

Samples were first prepared with the ratio of water/gypsum for the gypsum matrix as 50/100, 55/100, 60/100, 65/100 and 70/100. The water/gypsum

ratio of the mixture prepared for the gypsum-fiber composites was determined as 0,65 as this made the casting easier during the application.

Standard samples were produced with a dimension of 40 x 40 x 160mm and were left to dry in a 40°C drying-oven for 7 days. For experiments made to determine the modulus of elasticity and toughness values, the samples prepared were  $\Phi 75$  mm x 150 mm. For determining the impact strength test 10 x 10 x 160 mm samples were produced (Fig. 1 a-b). The homogeneous dispersion of the rPET fibers in the gypsum matrix can be seen clearly in the photographs.

## 2.2. SEM Analysis

SEM analysis were made to analyze the micro structures of the rPET fibers used as reinforcement phases with the gypsum matrix in the composites. Thus, a clearer information will be obtained about the interaction, adherence and the behavior of the fibers between gypsum and fiber. SEM analyses were made in the ITU Nano/Micro Electromechanical Systems Laboratory and Material Laboratory of the Trento University in Italy. The mechanical tests were conducted with Seidner Form+Test Compression Testing Machine with bending press (10 kN) and compression press (200 kN). The impact strength tests were investigated on a CEAST 2000, by the Charpy method, on notched specimen. TS EN 13279-1, TS EN 13279-2 standards were used in all tests. The surfaces of ruptures were gold-sputtered for microscopy observations by means of a Field Emission Scanning Electron Microscope (FE-



**Figure 1.** rPET fiber-gypsum composite samples.

SEM, Supra 40, Zeiss) for microstructural analysis.

### 3. Results and discussion

#### 3.1. Mechanical properties of gypsum-rPET fibers composites

Mechanical resistance strength of fiber-reinforced composites changes in relation to the adherence between the matrix and the phase. The fibers are bound together and are held aligned in the important stressed directions by matrix. Through the matrix, the principal load bearing elements are fibers, and these loads are transferred to the fibers by the matrix. The efficiency of this transfer is related to the quality of the bond between the fiber and the matrix. The adherence between the surface of the fibers and the matrix must be strong and the matrix must be able to transform the shear stress to the fibers (Özkul, 2016). Accordingly, critical fiber length gains importance for the composites reinforced with staple fibers. In situations where fibers shorter than the critical fiber length are used, the fibers do not have a strengthening effect in the composite. Additionally, if the adherence between the fiber and the matrix is weak, the fibers get out of the matrix and are separated. The critical fiber length of the rPET fiber that will be used for tests is calculated by the Kelly-Tyson correlation given in Formula 1 (Erdem, 2013). Here,  $l_{crit}$  represents critical fiber length,  $\sigma$  the tensile strength of the fiber,  $d$  the diameter of the fiber and  $\tau$  the shear stress. The critical fiber length has been calculated as 10 mm according to this.

$$(1) \quad l_{crit} = \frac{\sigma d}{2\tau}$$

Another approach in determining the critical fiber length was used and gypsum composites reinforced with rPET fibers were produced with the

same volume ratio (1%) and with different lengths (10, 20, 30 and 40mm). Adherence-enhancing additives were not added into these samples. Table 1 includes weight per unit of volume and flexural strengths of these composites.

As seen in Table 1, the weight per unit of volume of the reference gypsum is measured as 1,16 gr/cm<sup>3</sup>. It is observed that the weight per unit of volume value of the gypsum composites decreases due to the addition of fibers. Additionally, the flexural strengths of the composites decrease as the fiber length increases. Eve, et al. (2002) analyzed the properties of gypsum composites reinforced with different lengths of polyamide fibers and determined that as fiber lengths increase, the fibers were not dispersed homogeneously in the matrix and thus the flexural strengths of the samples decrease. The reason for this decrease was explained by the increase in the capillary structure of the composites (Eve et al., 2002). Similar results were achieved in this study as well. With the addition of the rPET fiber, the capillary structure of the composite increased, as the fiber length increased, the fibers were not dispersed homogeneously. It was determined that the sample prepared with the 10mm fiber had the highest flexural strength. Results of experimental studies also prove that the critical 10 mm fiber length determined by calculations is the right decision.

Figure 2 shows the weight per unit of volume graph of samples. The weight per unit of volume of the reference gypsum without fiber is 1,12 gr/cm<sup>3</sup>. It is seen that as the fiber ratio increases, the values of samples with 3,3 dtex do not change. There is an insignificant increase to 1,13 gr/cm<sup>3</sup>e in the values of the samples with %0,75, %0,1, %0,15, %0,2 and % 0,5 fiber in volume. The reason for this situation is believed to be the increasing capillary structure

**Table 1.** Flexural strength values of gypsum composites reinforced with fibers of different lengths.

Fiber Length (mm)	Fiber Volume Ratio (%)	Fiber Diameter (dtex)	Weight per Unit of Volume (gr/cm <sup>3</sup> )	Flexural Strength (N/mm <sup>2</sup> )
0	0	0	1,16	4,43
10	1	6	1,12	4,51
20	1	6	1,09	3,57
30	1	6	1,13	3,88
40	1	6	1,13	3,85

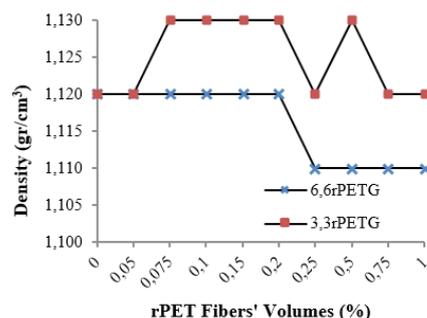


Figure 2. Graph showing weight per unit of volume of composites.

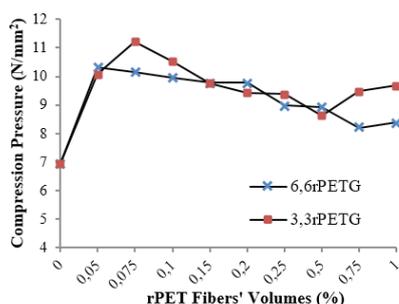


Figure 3. Graph showing compressive strength of composites.

due to the increase in the fiber volume ratio. It was determined that sample values of 3,3 dtex fiber composites and reference gypsum sample without fiber were the same, 1,12 gr/cm<sup>3</sup> between the ratios 0,05% and 0,2%. As per volume, between the ratios %0,25 and %1, the weight per unit of volume of samples containing 6,6 dtex fiber decreased a little and was determined as 1,11 gr/

cm<sup>3</sup>. Table 2 shows test results belonging to composites containing 10mm long 3,3 and 6i6 dtex rPET fibers and reinforced with PVA based adherence enhancing additives.

The compressive strength of the reference gypsum without fiber is 3,1 N/mm<sup>2</sup>. Although there is a decrease in the compressive strengths of the composites due to the increase in the fiber volume ratio, it is determined that these values are higher than those of the reference gypsum without fiber. With the addition of the fiber, the compressive strength of the gypsum has increased almost 62% (See Fig. 3). The sample with the highest value has 0,075% fiber by volume. It is believed that the fibers counterbalance the horizontal tensile stress and prevent the shear stress and horizontal swellings formed in the composites. Therefore, it can be said that the mechanical resistance of the composites has increased. Siddique et al. (2008), in a citation from Soroushian et al. (2003), stated that the compressive strengths of concrete composites reinforced with recycled polymer fibers increased a small amount (Siddique et al., 2008).

Figure 4 shows the test results of the three-point bending method carried out on the composites with a dimension of 40x40x160 mm. The effect of fiber addition is seen clearly in case of flexion. Additionally, fibrous charac-

Table 2. Properties of rPET fiber-gypsum composites.

Fiber Volume Ratio (v %)	Adherence Enhancing Additive Ratio (w %)	Fiber Diameter (dtex)	Weight per Unit of Volume (gr/cm <sup>3</sup> )	Flexural Strength (N/mm <sup>2</sup> )	Compressive Strength (N/mm <sup>2</sup> )	Charpy Impact Value (10 <sup>-6</sup> KJ/m <sup>2</sup> )	Modulus of Elasticity (N/mm <sup>2</sup> )	Toughness (J)
0	0	0	1,12	3,1	6,92	2,5	1184	0,4
0,05	5	3	1,12	4,0	10,07	2,7	2459	1,7
		6	1,12	4,5	10,3	2,8	1689	1,6
0,075	5	3	1,13	4,2	11,22	2,8	2578	1,9
		6	1,12	3,9	10,2	2,7	2244	1,9
0,1	5	3	1,13	4	10,52	2,8	2724	2,3
		6	1,12	3,3	10	2,7	2600	1,9
0,15	5	3	1,13	3,9	9,75	2,7	3070	2,3
		6	1,12	3,9	9,8	2,8	2575	2
0,2	5	3	1,13	4,1	9,41	2,9	3103	2,3
		6	1,12	3,9	9,8	2,8	2709	2,1
0,25	5	3	1,12	3,9	9,39	3,1	3266	2,6
		6	1,11	3,9	9	2,8	3094	2
0,5	5	3	1,13	3,9	8,63	4	3556	2
		6	1,11	4,0	8,9	3,2	3134	2
0,75	5	3	1,12	4,1	9,48	4,2	3748	2,2
		6	1,11	3,4	8,1	3,5	3491	2,5
1	5	3	1,12	3,6	9,68	5,5	4600	2,8
		6	1,11	3,7	8,4	4,7	3619	2,4

teristics such as the type, form, slenderness ratio and volume ratio of the fiber play an important role in toughness (Ersoy, 2001). In this study, the flexural strength values of all composites have increased with the addition of the fiber. The highest flexural strength value is 4,47 N/mm<sup>2</sup> and this was determined in the 0,05% fiber by volume composites with 6,6 dtex fiber. Nevertheless, as the fiber proportion increased, the flexural strength of composites decreased a little. Similarly, Eve et al. (2002), in their study analyzing the gypsum composites with polyamide fibers, expressed that the flexural strength of composites decreased with the increase in fiber by volume ratio and that samples including polyamide fiber between 0% and 1% by volume have the highest value (Eve et al., 2002).

When Table 1 and Table 2 are analyzed, the positive effect off adherence-enhancing additives on the flexural strengths of fiber reinforced composites are clearly seen. In Table 1, it is seen that in comparison with the reference gypsum without fiber, there is an insignificant increase in the flexural strength values of the composites with fibers with no adherence-enhancing additives. However, in Table 2 it is seen that with the addition of the adherence enhancing additives there is a 42% improvement in the flexural strength values. It is determined that the adherence-enhancing additive surrounds the fibers and improves the adherence between fiber and gypsum that is weak and decreases the porosity of the matrix.

In fiber-reinforced composites, not only the volume ratio, but also the diameter of the fiber influences the mechanical endurance of the composites. As the length/diameter ratio of the fibers increase the amount of weight transferred to the fibers by the matrix also increases. When sufficient interface bond is provided for the composites produced by small diameter fibers, higher strength is achieved than the composites reinforced with large diameter fibers (Şahin, 2006). It is determined here as well that the toughness of samples with 3,3 dtex fibers are higher than the others.

Charpy impact test results involving

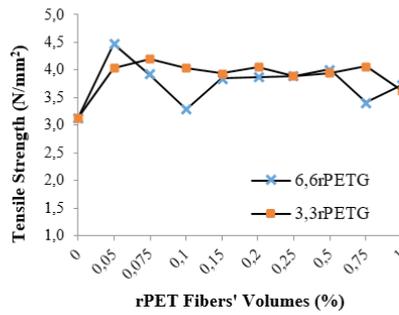


Figure 4. Flexural strength of composites graph.

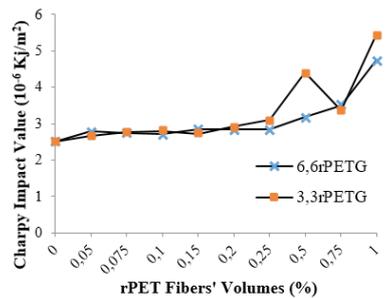


Figure 5. Charpy impact value of composites graph.

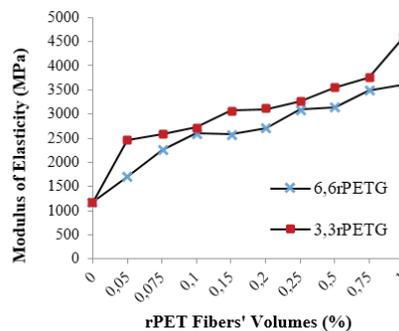


Figure 6. Modulus of elasticity of composites.

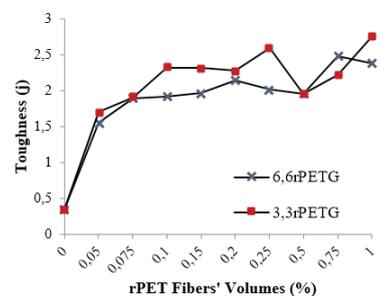


Figure 7. Toughness of composites.

10x10x160 mm composites are shown as graphics in Figure 5. As expected, as the fiber volume ratio increases, the impact resistance values of composites also increase. Impact value is improved almost twice and the highest impact value belongs to the composites

with the highest amount of fiber (1%). The fact that the gypsum composite has a higher impact resistance in comparison to reference gypsum without fiber can be explained with the “Gordon-Cook” theory. The impact power is directed towards the direction of the fiber when approaching the fiber. A large part of the deformation power is transformed into tensile strength and friction. Because of this, shear stress is created between the fiber and the matrix and this situation continues until the adherence between the fiber and the matrix is weakened (Ersoy, 2001). The use of adherence enhancing additives in this study strengthens this situation and consequently decreases considerably the brittleness of the gypsum.

It is seen in Figure 6 that the modulus of elasticity values of the composites increase as the amount of fiber increases. It is determined that composites with 1% of fiber volume have the highest modulus of elasticity values. Pursuant to the static modulus of elasticity correlation, although tensile strengths of composites with different fiber volume proportions do not change significantly, deformation decreases because of the increase in fiber and hence causes an increase in the modulus of elasticity. Figure 7 shows the toughness values of the composites. As the amount of fiber increases, there is an increase in the toughness values also increase, like the modulus of elasticity. This increase is an expected result in all fiber-reinforced composites. The impact strength of the gypsum samples is increased with rPET fibers. The toughness value of the reference gypsum sample without fiber was increased 7 times following the addition of fibers. When the toughness values of the composites with the lowest fiber ratio (0,05% of volume) and the composite with the highest fiber ration (1% of volume) are compared, there is approximately a 62% improvement. Fibers prevent the micro cracks from developing into macro cracks in the composites under stress and thus prevent sudden fractures in composites because of compression and impact. Toughness value results calculated by the stress deformation graph support the results of the Charpy impact test.


Like all other composites with brittle matrix and ductile fibers, the power holding characteristic of the material increases toughness under pressure (Ersoy, 2001). Similarly, Parres (2009) stated that under impact the brittleness of gypsum reinforced with polyamide fibers obtained from wasted tires decreases with the addition of fibers (Parres et al., 2009).

Still, it is stated that no matter how strictly the production conditions are controlled, composites are generally among materials with highest failure rate (Aran, 1990). It is known that the amount of these failures change in relation to production methods. For example, manually produced composites have the highest rate of failure. Additionally, in fiber reinforced composites, failure occurs due to following reasons: the average fiber volume ratio being small, misplacement or breaking of the fiber, presence of fibers not dispersed homogenously and dense parts in the matrix, delamination, errors due to setting of the material, resin cracks formed during cooling at the end of the production and errors due to the presence of areas with fibers undampened by the matrix (Aran, 1990). Likewise, it is stated that these failures lower the strength of the composite materials and the drop gets bigger by the increase of strain.


In this study, many unfavorable situations in line with the above-mentioned views have been encountered. The gypsum paste was first mixed with a mixer but it was observed that the fibers stuck to the mixer and formed balls and did not disperse homogeneously. Therefore, the method of manual production was preferred to mix the gypsum paste and the mixing of fibers into the gypsum paste. However, the above-mentioned failures occurred in the gypsum composite and accordingly, there were drops in the mechanical strengths of the composite samples.

### 3.2. Morphology of gypsum-recycled PET fiber composites


The micro analysis of gypsum composites and the dispersion of fibers in the matrix was carried out by scanning electron microscope (SEM). When the reference gypsum without fiber in Fig-

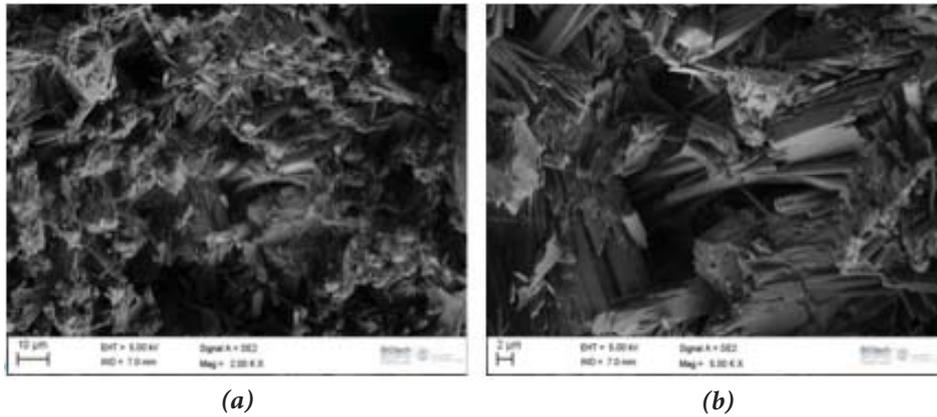

**Figure 7.** SEM photographs of reference gypsum samples without fiber magnified (a) 2.00 KX, (b) 5.00 KX times.

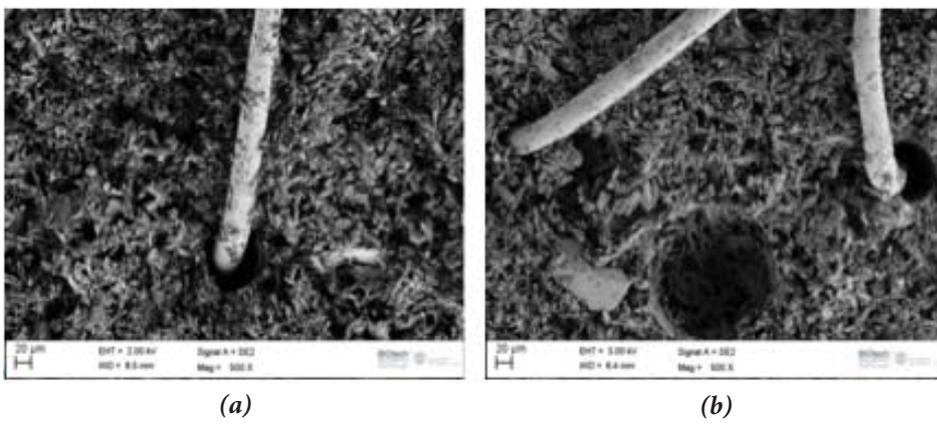

**Figure 8.** SEM photographs magnified 500 X times of gypsum composites reinforced with 6,6 dtex rPET fibers and without adherence-enhancing additives.

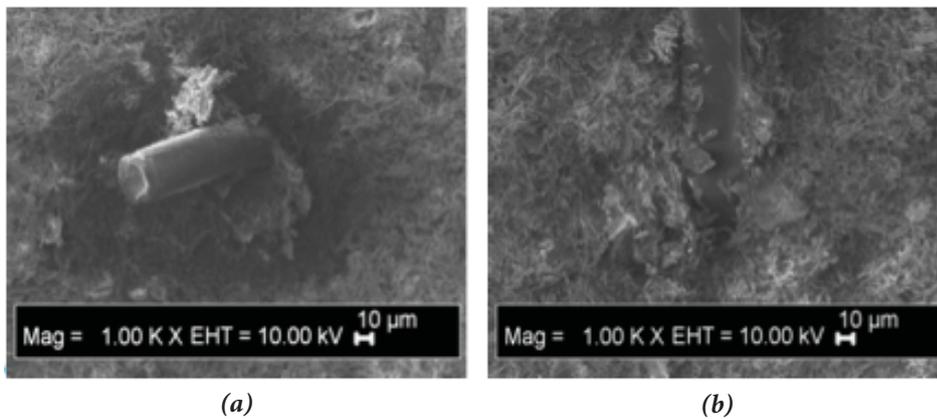


**Figure 9.** SEM photographs magnified 1.00 KX times of gypsum composites reinforced with 3,3 dtex rPET fibers and with adherence-enhancing additives.

ure 7a-b is analyzed, small needle-like crystals inside the gypsum is seen. These crystals have a complex layout and a random orientation. When the microstructure of the gypsum was analyzed in other studies small needle-like crystals were similarly observed (See Eve et al. 2007).

Figure 8 shows the SEM images of gypsum composites containing only fiber and without adherence-enhanc-

ing additives. In these photographs the crystalline microstructure of the fiber, rPET fibers, dehydrate crystals adhered to the fibers and details of the bond between the fiber and the gypsum are seen.

In the preliminary tests, moisture-free fibers were used in the gypsum paste but as they did not disperse homogeneously, uncut and unfinished rPET fibers were procured from the

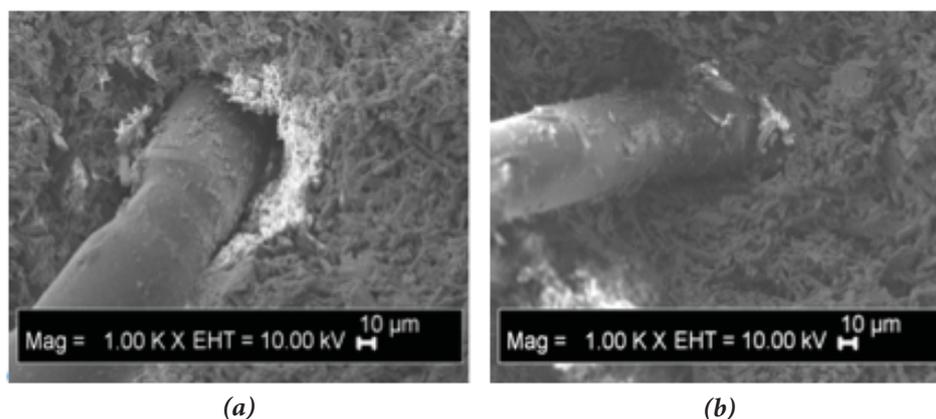

**Figure 10.** SEM photographs magnified 1.00 KX times of gypsum composites reinforced with 6,6 dtex rPET fibers and with adherence-enhancing additives.

company. These moist fibers were cut according to the critical fiber length and were used in the composite. However, the use of moist fibers created a problem. During the sample production process, following the drying of composites in the drying-oven, the fibers lost some of the water they contained and because of the decrease in volume the fibers shrunk and voids were formed around them. Although the dehydrate crystals adhered to the fibers show some amount of adherence between the gypsum matrix and the fibers, the presence of voids around the fibers indicate the weakness of the adherence between the fiber and the gypsum matrix (See Figure 8a-b). In other words, it is believed that adequate adherence between the gypsum matrix and the fibers was not achieved because of these voids. Similar results were found in literature research (Eve et al., 2007).

In Figures 9 and 10 the dispersion of the rPET fibers inside the gypsum composites that contain adherence-enhancing additive. The voids seen around the fibers in Figure 8 are not seen in these composites because of the added adherence-enhancing additives.

Rubio-Avalos et al. (2005) have stated that by the addition of styrene-butadiene latex additives into the gypsum, the capillary voids in the gypsum matrix are filled and this additive coats the surfaces of the gypsum crystals, and forms a polymer film layer, in other words a polymer mesh layer inside the matrix. Thus, under strain, the spread of micro cracks in the composites is prevented and the flexural strength of the composites is increased (Ru-

bio-Avalos et al., 2005). Here as well, it can be said that, following the addition of the adherence enhancing additive, a polymer film layer was created inside the gypsum matrix similarly and the adherence enhancer surrounded the fibers and increased the adherence between the gypsum and the fibers. Following this improvement, the mechanical strength of the composites has increased.

#### 4. Conclusion

Studies made to decrease the use of raw material resources to produce building materials and the energy used for the production-consumption processes, to minimize the direct or indirect harm given to the environment, gain more importance every day. In this study, fiber from wasted PET bottles was added into the gypsum matrix and a composite material was designed and produced in lab scale. Thus, the aim was to achieve both economic and ecologic benefits and to improve properties of gypsum such as the low impact strength-toughness value. In the tests carried out, first rPET fibers in different lengths were added into the gypsum matrix and the flexural strength values of these composites were determined and compared. Their strength values were observed to be lower than the gypsum without fiber. In tests made for a homogenous mixture and to determine the fiber length, it was observed that as the fiber length increased, the fibers were not dispersed homogeneously in the composite and accordingly their strength values dropped. It was decided that the best way to prevent fibers forming lumps in the mixture was to

leave the fibers in water before the mixing process and ensure their homogeneous dispersion. As a result of these tests, critical fiber length was determined to be 10 mm. When it was determined that the adherence between the fiber and the gypsum was not adequate, adherence enhancing additives were added to the composite. In the micro analysis, when the additive was added it was observed that the adherence enhancer surrounded the fibers, increased the bond between the fibers and the gypsum and improved adherence. In other words, it was observed that voids that decreased the adherence and the strength were not created around the fibers. In measurement performed under these conditions, a significant increase in the mechanical strengths of the composites was determined. Thus, an improvement of 60% in the compressive strength and 40% in the flexural strength of the composites were achieved. It is also believed that in flexural strength, the fibers met horizontal tensile stress and prevented the shear stress and horizontal swelling formed in the composites. The best performance was achieved with composites containing 0,1% fiber by volume. The use of fiber and adherence enhancer together improved more than expected the toughness and impact resistance values of gypsum. The toughness value increased almost 7 times while the impact resistance value increased twice. The modulus of elasticity also increased significantly. These results are believed to be guiding for studies made to solve problems developing due to the use of wasted fiber in the composites. It is believed that the compressive strengths of composites may be improved by the production of composites with the fibers placed orderly in a single direction instead of a random dispersion. When the fibers are dispersed angularly, when force is applied perpendicularly to direction of the fiber, the fibers act like voids in the composites and some amount of decrease is seen in the strength of the composites (Arioğlu et al., 2008). However, when force is applied perpendicular to the fibers, the reaction of the fibers will change. Therefore, laying down the fibers biaxial and uni-

formly in the composites must also be researched.

### Acknowledgements

The authors gratefully acknowledge Prof. Dr. Erol Gürdal, Prof. Dr. Claudio Migliaresi, Assoc. Prof. Dr. Levent Trabzon, Dr. Serkan Yatağan, Dr. Dario Zeni, İbrahim Öztürk, Prof. Dr. Ergin Arioğlu, Zehra Kundak, Mümin Balaban and for their helpful participation and also appreciate the hospitality of the Department of Materials and Industrial Technologies at the University of Trento, Italy.

### References

- Ahmad, I., Mosadeghzad, Z., Daik, R. and Ramli, A. (2008). The effect of alkali treatment and filler size on the properties of sawdust/UPR composites based on recycled PET wastes, *Journal of Applied Sciences*, 109, 3651–3658.
- Aran, A. (1990). *Elyaf Takviyeli Karma Malzemeler*, [Fiber Reinforced Composites], İstanbul: İstanbul Technical University Rectorship Offset Shop, Turkey.
- Arioğlu, E., Yüksel, A., Yılmaz, A., O. (2008) *Püskürtme Beton, Bilgi Föyleri-Çözümlü Problemler*, [Shotcrete, Data Sheets- Problems with Solutions], Chamber of Mining Engineers of Turkey Publishing No:142, İstanbul.
- Ersoy, H. Y. (2001). *Kompozit Malzeme*, [Composite Materials], İstanbul: Literatür Publishing.
- Eve, S., Gomina, M., Hamel, J. & Orange, G. (2002). Microstructural and mechanical behaviour of polyamide fibre-reinforced plaster composites, *Journal of the European Ceramic Society*, 22, 2269-2275.
- Eve, S., Gomina, M., Ozouf, J. C. & Orange, G. (2007). Microstructure of latex-filled plaster composites, *Journal of the European Ceramic Society*, 27, 1395-1398.
- Lei, Y., Wu, Q., Clemons, C. and Guo, W. (2009). Phase structure and properties of poly(ethylene terephthalate) / high-density polyethylene based on recycled materials, *Journal of Applied Polymer Science*, 113, 1710–1719.
- Özkul, H., (2016). *Composite Materials Lecture Notes*, İstanbul Technical University, Turkey.

- Erden, S. (2013). Geri dönüştürülmüş PET lifi-alçı kompozitlerin özelliklerinin belirlenmesi, [An analysis of the properties of the recycled PET fiber-gypsum composites], (Ph.D. Thesis), Istanbul Technical University, Turkey.
- Parres, F., Crespo-Amorós, J. E. and Nadal-Gisbert, A. (2009). Mechanical properties analysis of plaster reinforced with fiber and microfiber obtained from shredded tires, *Construction and Building Materials*, 23, 3182-3188.
- Rubio-Avalos, J. C., Manzano-Ramírez, A., Luna-Bárceñas, J. G., Pérez-Robles, J. F., Alonso-Guzmán, E. M., Contreras-García, M. E. & González-Hernández, J. (2005). Flexural behaviour and microstructure of a gypsum-SBR composite material, *Materials Letters*, 59, 230–233.
- Siddique, R., Khatib, J. and Kaur, I. (2008). Use of recycled plastic in concrete: a review, *Waste Management*, 28, 1835-1852.
- SUDER (<http://www.suder.org.tr>)
- Şahin, Y. (2006). *Kompozit Malzemelere Giriş*, [Introduction to Composite Materials], Ankara: Seçkin Publishing.