



Kabul Edilmiş Araştırma Makalesi (Düzenlenmemiş Sürüm)

Accepted Research Article (Uncorrected Version)

Makale Başlığı / Title

Investigation of the effects on rheological and filtration properties of water-based drilling mud of boron minerals: An experimental study

Bor minerallerinin su bazlı sondaj çamurunun reolojik ve filtrasyon özellikleri üzerindeki etkilerinin incelenmesi: Deneysel çalışma

Yazarlar / Authors

Abdullah ÖZKAN1*, Behlül Merve KAPLAN2

Referans No / Reference No

PAJES-89990

DOI

10.5505/pajes.2019.89990

Bu PDF dosyası yukarıda bilgileri verilen kabul edilmiş araştırma makalesini içermektedir. Sayfa düzeni, dizgileme ve son inceleme işlemleri henüz tamamlanmamış olduğundan, bu düzenlenmemiş sürüm bazı üretim ve dizgi hataları içerebilir.

This PDF file contains the accepted research article whose information given above. Since copyediting, typesetting and final review processes are not completed yet, this uncorrected version may include some production and typesetting errors.



Abstract (mirrored text)

Abdullah ÖZKAN, Behlül Merve KAPLAN

^{1,2}Department of Petroleum & Natural Gas Engineering, Iskenderun Tech University, Hatay, Turkey.
abdo.ozkan@gmail.com, behlulmervekaplan@gmail.com

Received / Kabul Tarihi: 14.11.2018; Accepted / Kabul Tarihi: 07.03.2019
* Corresponding author

doi: 10.5505/pjes.2019.89990
Research Article

Abstract

The aim of this study is to determine the effect on the rheological filtration properties of water based drilling fluid of boron minerals. For this purpose, water based drilling mud was prepared and borax, ulexite and colemanite concentrations (5% w/v) are separately added. The characteristics of borax, ulexite and colemanite are examined using fluorescence spectrometer (XRF). The rheological properties such as plastic viscosity, yield point and gel strength of the mud systems adding boron minerals were determined with viscometer. The filtration properties were measured using an API Filter Press. All physical measurements were carried out according to American Petroleum Institute (API) standards. Borax, ulexite and colemanite added (5% w/v) drilling muds rheological and filtration properties then compared with other and the additive free water based drilling mud. The rheological and filtration properties of developed mud systems are compared to original (additive free) system and with each other respectively. It is observed that additives improve the rheological properties of the drilling mud. Borax and colemanite have a better effect compared to ulexite. Filtration properties such as filtrate loss and filter cake thickness are compared to the original mud system but still in the acceptable range and can be implemented to drilling operations.

Keywords: Boron minerals, Water based drilling fluid, Drilling mud, Rheological properties, Filtration loss

Öz

Borun minerallerinin su bazlı delme sıvısının reolojik ve filtrasyon özellikleri üzerindeki etkisini incelemek amacıyla su bazlı delme sıvısı hazırlanmış ve boraks, üleksit ve kolemanitin her biri için %5 (w/v) konsantrasyonlarda ayrı ayrı eklenmiştir. Boraks, üleksit ve kolemanitin özellikleri floresan spektrometresi (XRF) kullanılarak araştırılmıştır. Reolojik özellikler (plastik viskozite, kayma gerilimi ve jel kuvveti) viskozimetre ile belirlenmiştir. Filtrasyon özellikleri ise API Filtrasyon Presi kullanılarak ölçülmüştür. Tüm fiziksel ölçümler Amerikan Petrol Enstitüsü (API) standartlarına göre yapılmıştır. Boraks, üleksit ve kolemanitin (5% w/v) eklenmiş delme sıvılarının reolojik ve filtrasyon özellikleri diğer delme sıvılarına ve katkı maddesiz su bazlı delme sıvısına karşılaştırılmıştır. Reolojik ve filtrasyon özellikleri geliştirilmiş delme sıvıların orijinal (katkı maddesiz) sistemle ve birbirleriyle karşılaştırılmıştır. Katkı maddelerinin delme sıvısının reolojik özelliklerini iyileştirdiği gözlemlenmiştir. Boraks ve kolemanitin üleksiteye göre daha iyi bir etkiye sahiptir. Filtrasyon özellikleri (filtrat kaybı ve filtre tortu kalınlığı) orijinal delme sıvısına karşılaştırılmıştır ancak kabul edilebilir sınırlarda kalmıştır ve delme işlemlerinde uygulanabilir.

Anahtar kelimeler: Borun mineralleri, Su bazlı delme sıvısı, Delme sıvısı, Reolojik özellikler, Filtrasyon kaybı

1 Introduction

Petroleum exploration activities are expanding as the energy demand increase. There are many reports about the drilling operations both in economically and technically. Drilling fluids account for approximately 10 % of the drilling costs. Technological developments lead to highly efficient and cost effective drilling fluid explorations. In a drilling operation, drilling mud is one of the main components to remove rock fragments from the wellbore to implement necessary hydrostatic pressure to cool and lubricate whole systems and to ensure the stability of the hole [1]. Drilling mud is grouped mainly as water based, oil based and air based, while water based mud is widely used in the industry [2]. Water based drilling fluid includes in water, bentonite, viscosity reducer, fluid loss reducer etc. [3]. To improve drilling operations, a convenient drilling fluid is used. Many reports have shown that the related properties of drilling fluids are improved by some additives including polymers and nanomaterials [4,6]. Industrial minerals including nano and micro size particles

have been used as a mud additive to improve rheological properties of the drilling fluid [7],[8]. Boron minerals such as colemanite and ulexite have been the subject of numerous patents in the energy industry in oil and gas exploration, drilling and well completion [9],[10]. For example, a water based drilling mud of colemanite (C₁₀H₁₁O₇) in the form of a hydrate (C₁₀H₁₁O₇·nH₂O) has been used as a mud additive to improve rheological properties [11]. In this study, The rheological properties of the developed mud systems such as plastic viscosity (PV), apparent viscosity (AV), gel strength were investigated by FANN 35 viscometer while filtration properties were investigated by API filter press. Filtrate loss and cake thickness was analyzed using an American Petroleum Institute (API) fluid loss testing equipment [12].

2 Experimental procedure

2.1 Sample preparation

Water based fluids are the common drilling mud used in the oil industry. Water is the continuous phase, providing the initial

rheological properties of the drilling fluid. First, in order to prepare the water based drilling fluid, bentonite and barite were provided from the Turkish Petroleum Corporation (TPAO). Mineral borax ($\text{Na}_2\text{B}_4\text{O}_7 \cdot 10\text{H}_2\text{O}$) with the particle size of 45 μm , mineral ulexite ($\text{Na}_2\text{CaB}_6\text{O}_{11} \cdot 8\text{H}_2\text{O}$) with the particle size of 75 μm and mineral colemanite ($\text{Ca}_2\text{B}_6\text{O}_{11} \cdot 5\text{H}_2\text{O}$) with the particle size of 100 μm were obtained from Turkish Boron Institute. Water based drilling fluid (WBDF) system was prepared by using fresh water, bentonite (5 wt %) and barite as a densifier. The pH value of the fluid was adjusted by sodium hydroxide (NaOH). After preparation of the mud, the system was mixed for 30 minutes in total. This drilling fluid was used as an arbitration specimen. Secondly, same drilling fluid was prepared by adding various amounts of borax, ulexite and colemanite (1, 2, 3, 4 and 5 wt %). The mixture was mixed for 3 minutes and then aged for 16 hours (average temperature 25 °C). Conventional WBDF and borax, ulexite and colemanite added WBDF formulations are given in (Table 1).

Table 1: Formulations of the developed mud systems

Materials	WBDF	Borax, Ulexite and Colemanite added WBDF (w/v %)				
		1 %	2 %	3 %	4 %	5 %
Bentonite (g)	22.8	22.8	22.8	22.8	22.8	22.8
Fresh water (g)	400	400	400	400	400	400
Barite (g)	11.4	11.4	11.4	11.4	11.4	11.4
NaOH (g)	1	1	1	1	1	1
Borax (g)	-	4.35	8.70	13.05	17.4	21.75
Ulexite (g)	-	4.35	8.70	13.05	17.4	21.75
Colemanite(g)	-	4.35	8.70	13.05	17.4	21.75

2.2 Characterization of the Bentonite, Borax, Ulexite and Colemanite

Chemical composition of the bentonite was determined by X-ray fluorescence (XRF) and shown in (Table 2). As expected the results showed that SiO_2 and Al_2O_3 were the main components in the structures and bentonite was suitable for the API Specification 13A standard [13],[14]. Chemical Compositions of borax, ulexite and colemanite are shown in (Table 3).

Table 2: Chemical composition of the bentonite

Sample	Content of Oxides (wt %)							
	Na_2O	MgO	Al_2O_3	SiO_2	K_2O	CaO	TiO_2	Fe_2O_3
Na-Bentonite	2.48	2.44	20.9	65.85	0.75	1.44	0.29	5.85

Table 3: Chemical compositions of borax, ulexite and colemanite

Material	Content of Oxides (wt %)			
	B_2O_3	CaO	Na_2O	H_2O
Borax	36.51	-	16.25	47.24
Ulexite	42.95	13.84	7.65	35.57
Colemanite	50.90	27.20	-	21.90

2.3 Analysis of the physical properties

The elemental compositions of the borax, ulexite and colemanite were determined by using an XRF instrument. The physical properties of the drilling mud were determined using a method based on API standard, including all filtration and rheological properties. The rheological properties such as apparent viscosity (AV), plastic viscosity (PV), yield point (YP) and gel strength of the boron minerals added to the drilling fluid were determined with a FANN viscometer. The filtration

properties were also examined using an API Filter Press. All physical measurements were carried out according to the American Petroleum Institute (API) standards. FANN viscometer was used to investigate rheological properties. API (American Petroleum Institute) Filter press was used to measure the filtration properties of the different solutions. Rheological properties were correlated according to the empirical formulas given below;

The filtration properties of solutions were also determined by an API (American Petroleum Institute) standard filter press equipment. 100 psi pressure was applied to the fluid column for 30 minutes and filtrate loss, as well as mud cake thickness, were measured. The density of the mud was also measured using mud balance method consisting of a base and balance arm with a cup for counterweight.

3 Results and Discussions

In this study, the effects of boron minerals addition such as borax ($\text{Na}_2\text{B}_4\text{O}_7 \cdot 10\text{H}_2\text{O}$), sodium calcium borate group ulexite ($\text{NaCaB}_6\text{O}_{11} \cdot 8\text{H}_2\text{O}$) and calcium borate group colemanite ($\text{Ca}_2\text{B}_6\text{O}_{11} \cdot 5\text{H}_2\text{O}$) respectively, to the rheological and filtration properties of water based drilling mud were examined. In addition, the results obtained were compared with the rheological and filtration properties of water based drilling mud consisting of only bentonite and water (additive free). All data in this study was given on Table 4. According to Table 4, the positive effect on rheological properties such as apparent viscosity, plastic viscosity, yield point and gel strength of the developed mud systems was obtained in comparison with API standards.

Table 4: Rheological and Filtration results of the drilling mud

Parameters	API standards	WBDF (free additive)	Boron minerals added WBDF (w/w%)														
			% 1			% 2			% 3			% 4			% 5		
			45	75	100	75	100	45	75	100	45	75	100	45	75	100	
PV (cP)	Min 7	11.5	12	9	13.3	12.5	9	14	13	9	14.1	13.5	10	14.8	17	10	15
YP (lb/100 ft ²)	Max 50	9	31	24	15	32	28	18	32	35	21	38	35	24	39	37	20
AV (cP)	Min 15	16	18.5	21	22.5	19.25	23	24	21.5	26.5	25.5	22	27.5	27	28.5	28.5	25
Gel at 10 second	15	11	10	24	10	11	25	13	14	29	15	16	34	15	23	35	20
Gel at 10 minute	31	35	23	31	33	24	32	33	25	34	34	30	35	35	33	42	39
Liquid loss (mL)	10-15	9.6	15.2	18	10	12.8	18	10.8	11.2	19.6	11.2	11.6	19.6	11.6	12.8	19.6	12.8
Cake thickness (mm)	4	0.20	0.21	0.23	0.25	0.25	0.25	0.32	0.28	0.31	0.42	0.30	0.35	0.48	0.33	0.40	0.50

3.1 Effect of the borax, ulexite and colemanite ratio on rheological and filtration properties of water based drilling fluids

Viscosity is generally defined as resistance to flow interaction directly with temperature, solids content, additives and preservatives incorporated into the mud and the pump force. Viscosity is measured in terms of apparent viscosity (AV), plastic viscosity (PV) and yield point (YP). AV is the viscosity of the fluid under a certain force or at a certain rate of flow. PV is a constant value that characterizes the flow region. YP is the initiating force. Viscosity values of the different boron additives and compositions are shown in the (Figure 1, Figure 2 and Figure 3)

sticking and slow rate of penetration [15], [16]. It is also noted that ulexite addition negatively affects plastic viscosity.

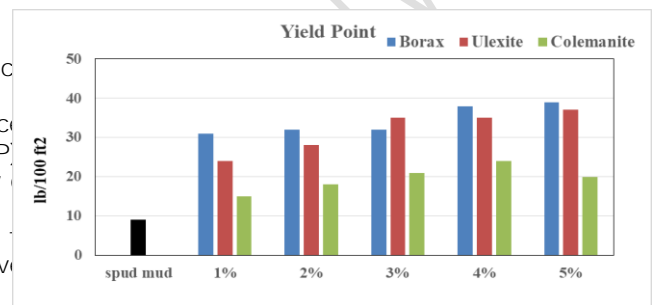


Figure 3 Yield points of the developed mud systems

The yield point is also important for the selection of pump and pressure needed to flow the mud from static positions [16]. All these boron minerals additions increase yield point of the mud; borax and ulexite increases the yield point 3 times than the original mud while the yield point tends to decrease after 4% colemanite addition.

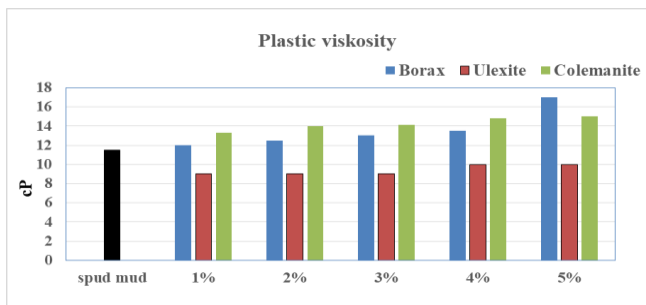


Figure 1: Plastic viscosities of the developed mud systems

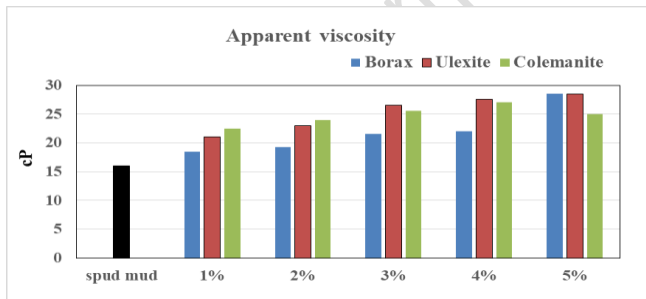


Figure 2 Apparent viscosities of the developed mud systems

Plastic viscosities of the mud increases as borax and colemanite concentrations in the mud increases, however, it is observed that plastic viscosity decreases with ulexite addition, after 3% ulexite concentration, plastic viscosity gets uptrend but still below the spud mud value. For the apparent viscosities, all three additives increase the apparent viscosity of the original mud with borax to be the most effective for the rise among others. It is seen that the addition of boron minerals into the drilling fluid could provide better flowability and reduce the possible problems such as surge, swab pressure, differential

In addition, as shown in the (Figure 4 and Figure 5) the developed mud systems had a high gel strength, which is desirable for eliminating problems in drilling operations such as poor hole cleaning, high torque and drag, pipe sticking, wellbore instability, lost circulation and formation damage [18].

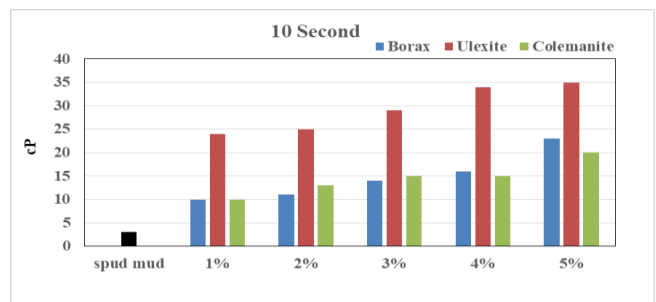


Figure 4: Gel strength (10 second) of the developed mud systems

For the 10 second gel strength, ulexite addition to mud shows a considerable effect, the value was 6 times higher than the original mud. Borax and colemanite additions also increase the gel strength of the developed mud systems but the effect is lower compared to the ulexite addition.

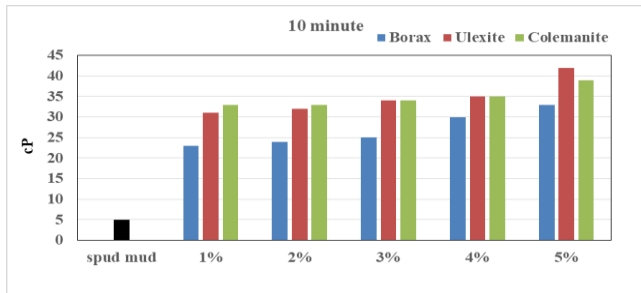


Figure 5: Gel strength (10 minute) of the developed mud systems

Both 10 seconds and 10 minutes gels strength values of the systems increase with the increasing concentrations. For the mud systems increases as particle size increases. Since ulexite and colemanite additions, the 10 minute gels strength increases with 1 % concentration, after that concentration the change is almost negligible from 1% to 4%, after 5% concentration the change in 10 seconds gel strength is visible as well.

It is desirable that the fluid loss rate of the drilling mud should be in the range of 10 mL, as the loss of fluid to be sustained by the continuously circulating mud in the borehole may cause the drilling equipment to get stuck in the well, lock the pipe and possibly overload. Filter cake thickness is also important to prevent significant borehole problems such as equipment sticking, wellbore stability and ensure that productive zones are not contaminated as well as the proper well log evaluation [19]. In this regard, the data obtained from the study given in the (Figure 6 and Figure 7)

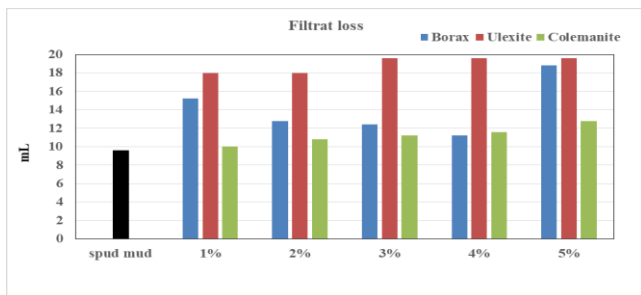


Figure 6: Filtrate loss of the developed mud systems

Filtrate losses of the developed systems are higher than of the original mud systems and they even keep increasing as the concentration increases. Ulexite addition gives most negative effect on filtration loss of the system with increasing the filtration loss by 83 % at an addition rate of 1 %. Colemanite addition shows the least effect on filtration properties. Filtration characteristic of the borax is different than of ulexite and colemanite. In the first place, borax addition of 1% to mud system increases filtration losses up to 15.2 ml from the original value of 9.8 ml. As the concentration is 2 %, 3 % and 4 %, filtration losses become 12.8 ml, 12.4 ml and 11.1, respectively.

The surfaces of the drilling mud and the filter cake are desired to be smooth and the cake thickness to be 1 mm (max 4 mm). Obtained cake thickness of the developed systems is given below.

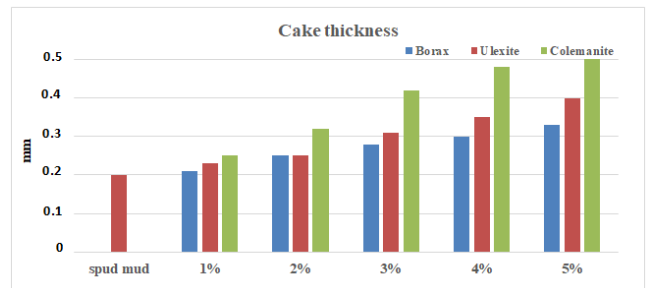


Figure 7: Filter cake thickness of the developed mud systems

Filter cake thickness of the developed mud systems are increases with concentration. Besides, filter cake thickness of the mud systems increases as particle size increases. Since borax has the minimum particle size with the 45 µm particle thickness of borax is lower than those of the others while 100 µm particle sized colemanite added mud system has the highest cake thickness.

Filtration properties of the mud systems are expected to improve as the particle size decreases, therefore, the addition of nano sizes of these materials should further investigated.

4 Conclusions

In this study, the effect of borax, ulexite and colemanite additions on the rheological and filtration properties of drilling mud was investigated. These aforementioned boron minerals were added into drilling mud at various concentrations as 1 % (w/v). Particle sizes of the additives were also different and borax, ulexite, and colemanite with particle sizes 45 µm, 75 µm and 100 µm of were added, respectively. Results show that rheological properties such as plastic viscosity (PV) and apparent viscosity (AP) of the drilling mud were improved with borax and colemanite additions while ulexite addition negatively affected plastic viscosity. Yield points of all three developed mud systems prepared with boron minerals were increased. Both 10 seconds and 10 minutes gels strengths of the systems increasing with increased with increasing concentrations. Filtrate losses and the filter cake thickness, which are not desirable for proper drilling operation, of the developed systems were found higher than those of the original mud systems and increased with the concentration increase. However, the filtrate loss and filter cake thickness of the developed systems are still in the acceptable value range. Filtration properties of the mud systems are supposed to be improved as the particle size decreases, therefore, the addition of nano sized boron minerals should be further investigated.

5 References

- [1] "Enhanced drilling fluids: a pioneering approach to overcome uncompromising drilling", *Journal of Energy Resources Technology*, 134(1), 014501, 2012.
- [2] "The rheological behaviour of aqueous calcium hydroxide suspensions", *Rheologica Acta*, 45(4), 425-434, 2006.
- [3] "Pressure rheology of water-based drilling fluids", *Journal of Petroleum Science and Engineering*, 19, 2011.
- [4] "Effect of polyether diamine in water-based drilling fluids", *Journal of Energy Resources Technology*, 134(1), 014501, 2012.

- Journal of Petroleum Science and Engineering* 78(5):15, 2011.
- [5] Amanullah, Y. et al. "Effect of additives to protect the marine environment from the Journal of Petroleum Science and Engineering" 43, 199208, 2005.
- [6] Filipović, M. et al. "The effect of fluids on coal permeability: Impact on horizontal wellbore International Journal of Coal Geology" 77:191, 2009.
- [7] J. A. E. S. et al. "Organosepiolite modified by different surfactants and their rheological behavior in oil Applied Clay Science" 159:94101, 2018.
- [8] J. A. E. S. et al. "Rheological properties of organosepiolite in oil Applied Clay Science" 154:431, 2018.
- [9] Eti Mine. *Kestelek colemanite. Product catalogue*, p.217. Ankara, Eti Mine Works General Management Publishing, 2014.
- [10] Eti Mine. *Milled colemanite. Product catalogue*. Ankara, Eti Mine Works General Management Publishing, 2014.
- [11] J. A. E. S. et al. "Effect of Sized Colemanite on the Rheological Properties of the Faculty of Engineering and Architecture" 33(4), 838, 2018.
- [12] S. L. et al. "Standard Practice for field testing of water American Petroleum Institute. ANSI/API 13B/ISO 10414:2003." 2003.
- [13] S. L. et al. "American Association of Drilling Engineers, Fluids conference and exhibition, Houston, Texas, 2010." 2010.
- [14] S. L. et al. "American Petroleum Institute, ANSI/API 13A/ISO 13500, 2010." 2010.
- [15] S. L. et al. "Applied Clay Science" 39(12), 1927, 2008.
- [16] S. L. et al. "Rheological properties of water Journal of Petroleum Science and Engineering" 100:1-8, 2012.
- [17] S. L. et al. "Progress in Energy and Combustion Science" 36(3), 32363, 2010.
- [18] Z. E. et al. "International Journal of Non-Dimensional" 5(5), 46371, (Special Issue) 2014.
- [19] Ersoy, A. "Kitabevi, Ankara. ISBN: 978 605 397 014 9, 2008." 2008.

Düzenlenmemiş Sürüm - Uncontrolled Version